

Doped Mott Insulators in (111) Bilayers of Perovskite Transition-Metal Oxides with a Strong Spin-Orbit Coupling

Satoshi Okamoto*

Materials Science and Technology Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, USA

(Received 1 October 2012; published 6 February 2013)

The electronic properties of Mott insulators realized in (111) bilayers of perovskite transition-metal oxides are studied. The low-energy effective Hamiltonians for such Mott insulators are derived in the presence of a strong spin-orbit coupling. These models are characterized by the antiferromagnetic Heisenberg interaction and the anisotropic interaction whose form depends on the d orbital occupancy. From exact diagonalization analyses on finite clusters, the ground state phase diagrams are derived, including a Kitaev spin liquid phase in a narrow parameter regime for t_{2g} systems. Slave-boson mean-field analyses indicate the possibility of novel superconducting states induced by carrier doping into the Mott-insulating parent systems, suggesting the present model systems as unique playgrounds for studying correlation-induced novel phenomena. Possible experimental realizations are also discussed.

DOI: 10.1103/PhysRevLett.110.066403

PACS numbers: 71.27.+a, 74.20.-z

Competition and cooperation between Mott physics and the relativistic spin-orbit coupling (SOC) have become a central issue in condensed matter physics. As these two effects become comparable, $4d$ and $5d$ transition-metal oxides (TMOs) could be ideal platforms to explore novel phenomena originating from such interactions. This brought considerable attention to iridium oxides [1–3]. Of particular interest is $A_2\text{IrO}_3$ ($A = \text{Li}$ or Na) where Ir ions form the honeycomb lattice. Density-functional-theory calculations for Na_2IrO_3 predicted the quantum spin Hall effect [4]. Alternatively, with strong correlation effects, the low-energy properties of $A_2\text{IrO}_3$ could be described by a combination of pseudodipolar interaction and Heisenberg interaction [5], called the Kitaev-Heisenberg model [6], which is a candidate for realizing Z_2 quantum spin liquid (SL) states. However, later experimental measurements confirmed a magnetic long-range order [7–9] in Na_2IrO_3 possibly because of longer-range magnetic couplings [10–12]. The effect of carrier doping into the Kitaev-Heisenberg model was also studied [13,14].

Interacting electron models on a honeycomb lattice have long been theoretical targets for realizing novel phenomena such as the quantum Hall effect without Landau levels [15] and the spin Hall effect with the SOC [16]. The spin Hall effect could also be generated by correlations without the SOC [17]. Yet, experimental demonstrations for such correlation-induced phenomena remain to be done. Recently, artificial bilayers of perovskite TMOs grown along the [111] crystallographic axis, where transition-metal ions form the buckled honeycomb lattice (Fig. 1), were proposed as new platforms to explore a variety of quantum Hall effects [18–20]. This proposal was motivated by the recent development in synthesizing artificial heterostructures of TMOs [21]. TMO heterostructures have great tunability over fundamental physical parameters, including the local Coulomb repulsion, SOC, and

carrier concentration. However, the effect of correlations to possible novel phenomena near Mott-insulating states with a strong SOC remains to be explored.

Here, we address the correlation effects in TMO (111) bilayers with a strong SOC. Specifically, we consider t_{2g}^5 systems and $e_g^{1,3}$ systems for which the low-energy electronic properties could be described in terms of $S = 1/2$ isospins [22]. We derive the effective Hamiltonians for such Mott insulators and analyze them numerically and analytically. The effective Hamiltonian for t_{2g}^5 has the form of the Kitaev-Heisenberg model [5], but the SL was found to exist only in a small parameter regime. On the other hand, the effective Hamiltonian for $e_g^{1,3}$ has the Ising-type anisotropy, thus the SL is absent. The effect of carrier doping is analyzed using slave-boson mean-field (SBMF) methods including *Ansätze* which reduce to exact solutions at limiting cases of zero doping. It is shown that carrier doping makes the physics of our model systems more interesting by inducing unconventional superconducting states, most likely $d + id$ pairing which breaks time-reversal symmetry.

Effective models.—We start from a multiband Hubbard model with t_{2g} orbitals or e_g orbitals. In both cases, only the nearest-neighbor hoppings are considered, and the

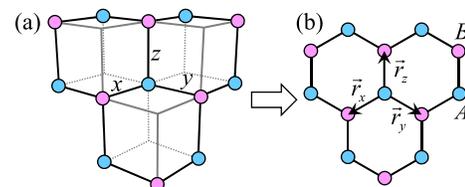


FIG. 1 (color online). Buckled honeycomb lattice realized in a (111) bilayer of the cubic lattice. x , y , and z in (a) indicate the cubic axes and the spin components in the Kitaev interaction on the buckled honeycomb lattice shown in (b).

hopping amplitude is derived from the Slater-Koster formula [23] with oxygen p orbitals located between the neighboring two d orbitals. The explicit forms of the multi-band Hubbard models are given in Ref. [24].

The low-energy effective Hamiltonian for t_{2g}^5 systems is derived from the second-order perturbation processes with respect to the transfer terms and by projecting the superexchange-type interactions onto the isospin states for $J_{\text{eff}}^z = \pm 1/2$ [24]:

$$|J_{\text{eff}}^z = \sigma\rangle = \frac{1}{\sqrt{3}}\{i|a, -\sigma\rangle - \sigma|b, -\sigma\rangle + i\sigma|c, \sigma\rangle\}. \quad (1)$$

Here, a , b , and c are the t_{2g} multiplet given by $|a\rangle = |yz\rangle$, $|b\rangle = |xz\rangle$, and $|c\rangle = |xy\rangle$, respectively. The effective interaction between sites \vec{r} and \vec{r}' along the γ bond (see Fig. 1) reads

$$H_{\vec{r}\vec{r}'}^\gamma = -J_0 + J_H \vec{S}_{\vec{r}} \cdot \vec{S}_{\vec{r}'} + J_K S_{\vec{r}}^\gamma S_{\vec{r}'}^\gamma. \quad (2)$$

$J_0 = \frac{1}{27}(15r_1 + 5r_2 + 4r_3)$, $J_H = \frac{8}{27}(3r_1 + r_2 + 2r_3)$, $J_K = \frac{4}{9}(r_1 - r_2)$, where $r_1 = t_\pi^2/(U - 3I)$, $r_2 = t_\pi^2/(U - I)$, $r_3 = t_\pi^2/(U + 2I)$. Here, both Heisenberg and Kitaev terms have positive sign, i.e., antiferromagnetic (AFM) [25].

For e_g systems in the (111) bilayers, the SOC is activated through the virtual electron excitations to the t_{2g} multiplet under the trigonal C_{3v} crystalline field [18,24]. Using the basis $|\alpha\rangle = |3z^2 - r^2\rangle$ and $|\beta\rangle = |x^2 - y^2\rangle$, a low-energy Kramers doublet for e_g^1 is given by

$$|\sigma\rangle = \frac{1}{\sqrt{2}}\{|\alpha, \sigma\rangle + i\sigma|\beta, \sigma\rangle\}, \quad (3)$$

where the spin quantization axis is taken along the [111] crystallographic axis. For e_g^3 , the + sign in Eq. (3) is replaced by the - sign. This doublet can be gauge transformed to $\frac{1}{\sqrt{2}}\{|3x^2 - r^2, \sigma\rangle + i\sigma|y^2 - z^2, \sigma\rangle\}$ and $\frac{1}{\sqrt{2}}\{|3y^2 - r^2, \sigma\rangle + i\sigma|z^2 - x^2, \sigma\rangle\}$ with trivial phase factors. Thus, the effective interaction is expected to be symmetric with respect to the bond direction. Following the same procedure for the t_{2g}^5 systems, the effective interaction between sites \vec{r} and \vec{r}' is derived as

$$H_{\vec{r}\vec{r}'} = -J_0 + J_H \vec{S}_{\vec{r}} \cdot \vec{S}_{\vec{r}'} - J_I S_{\vec{r}}^z S_{\vec{r}'}^z. \quad (4)$$

Here, $J_0 = \frac{1}{8}(3r_1 + 2r_2 + r_3)$, $J_H = \frac{1}{2}(r_1 + r_3)$, $J_I = \frac{1}{2}(2r_1 - r_2 - r_3)$, where $r_1 = t_\sigma^2/(U - 3I)$, $r_2 = t_\sigma^2/(U - I)$, $r_3 = t_\sigma^2/(U + I)$. Now the anisotropic term is described as a ferromagnetic (FM) Ising interaction. This comes from the fact that the total S^z is conserved in the model [see Eq. (3) and Ref. [24]].

The effect of the direct dd transfers [26,27], termed t_δ after $(dd\delta)$ bonding, for both the models is discussed in Ref. [24].

Undoped cases.—Here we discuss the AFM Kitaev-AFM Heisenberg (AKAH) model for the t_{2g}^5 system and

the FM Ising-AFM Heisenberg (FIAH) model for the $e_g^{1,3}$ system using the parametrization $J_H = 1 - \alpha$ and $J_{K,I} = 2\alpha$. As J_H and J_K have the same sign, the direct transition is expected between the Néel AFM at small α and the Kitaev SL at large α for the AKAH model. For the FIAH model, the planar Néel AFM is expected at small α and the FM with the spin moment in the [111] direction at large α .

We now employ the Lanczos exact diagonalization for the model Hamiltonians [Eqs. (2) and (4)] defined on a 24-site cluster with the periodic boundary condition. This cluster is compatible with the four-sublattice transformation [5] which changes the original spin S to \tilde{S} . Numerical results shown in Figs. 2(a) and 2(b) confirm the above considerations. Yet, the SL regime is found to be rather narrow for the AKAH model with the critical $\alpha_c \sim 0.96$ separating it from a magnetically ordered phase. For the FIAH model, the phase transition takes place at $\alpha = 0.5$ separating the (111) FM phase and the planar Néel AFM phase. In Refs. [27,28], the hypothetical Kitaev-Heisenberg models with different signs of interactions are studied.

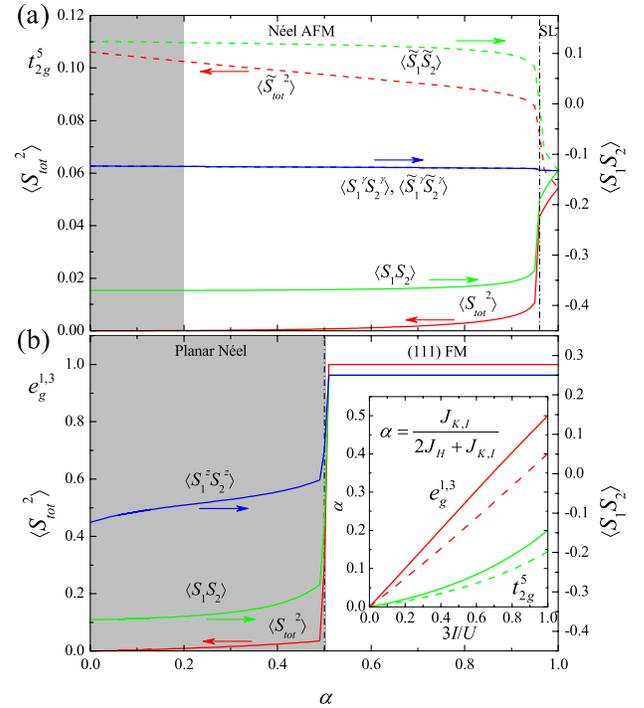


FIG. 2 (color online). Lanczos exact diagonalization results, squared total spins (normalized to its value in the fully polarized FM state), and the nearest-neighbor spin correlations, for t_{2g}^5 model (a) and $e_g^{1,3}$ model (b) obtained on 24-site clusters as a function of α . Solid (dashed) lines correspond to original (rotated) spin basis. Vertical dash-dotted lines are first-order phase boundaries. Shaded areas are the parameter ranges for $0 < 3I < U$ with $t_\delta = 0$. Inset: Controlling parameter α for both t_{2g}^5 and $e_g^{1,3}$ models as a function of $3I/U$. Dashed lines include $t_\delta = 0.1t_\pi$ or $t_\delta = 0.1t_\sigma$.

Natural questions arise, such as where is the “physical” parameter range, i.e., $U > 3I$, and can t_{2g} systems realize the Kitaev SL phase? Now, rewriting $J_{K,I}$ and J_H as $J_{K,I} = 2J\alpha$ and $J_H = J(1 - \alpha)$, respectively, with J the normalization, one obtains $\alpha = J_{K,I}/(2J_H + J_{K,I})$. In the inset of Fig. 2, we plot α for both the t_{2g}^5 and the $e_g^{1,3}$ models as a function of I/U . It is shown that α does not exceed $1/5$ for the AKAH model and $1/2$ for the FIAH model; thus both cases fall into the Néel ordered regime. The effect of the direct dd transfers is found to merely suppress the anisotropic interactions, as seen as dashed lines. Thus, additional interactions, such as magnetic frustrations, are necessary to realize the Kitaev SL phase in t_{2g} systems to suppress J_H .

Slave-boson mean-field theory.—Although the Kitaev SL phase is outside the “physical regime” for Mott-insulating systems, there could emerge novel electronic states by carrier doping [13,14]. As the two models are reduced to the tJ model on the honeycomb lattice at $\alpha \rightarrow 0$, one possible candidate is the singlet superconductivity (SC) with the broken time-reversal symmetry, so-called $d + id$ [29]. In the opposite limit of the AKAH model, novel SC states could be stabilized in connection to the Z_2 SL. For the FIAH model, on the other hand, the triplet (p) SC states may emerge. Here, we examine these possibilities using a SBMF theory.

First, we introduce a SBMF method that can be applied for Ising-like anisotropic interactions. An $S = 1/2$ spin operator for a Kramers doublet is described by fermionic spinons f_σ as $S_{\vec{r}}^\gamma = \frac{1}{2} f_{\vec{r}\sigma}^\dagger \tau_{\sigma\sigma'}^\gamma f_{\vec{r}\sigma'}$, with the local constraint $\sum_\sigma f_{\vec{r}\sigma}^\dagger f_{\vec{r}\sigma} = 1$ and $\hat{\tau}^\gamma$ being a Pauli matrix. Now, a spin quadratic term can be decoupled into several different channels as

$$S_{\vec{r}}^\gamma S_{\vec{r}'}^\gamma = -\frac{1}{8} (\Delta_{\vec{r}\vec{r}'}^* \Delta_{\vec{r}\vec{r}'} + \chi_{\vec{r}\vec{r}'}^* \chi_{\vec{r}\vec{r}'} + t_{\vec{r}\vec{r}'}^{\gamma*} t_{\vec{r}\vec{r}'}^\gamma + e_{\vec{r}\vec{r}'}^{\gamma*} e_{\vec{r}\vec{r}'}^\gamma) + \frac{1}{8} \sum_{\gamma' \neq \gamma} (t_{\vec{r}\vec{r}'}^{\gamma'*} t_{\vec{r}\vec{r}'}^{\gamma'} + e_{\vec{r}\vec{r}'}^{\gamma'*} e_{\vec{r}\vec{r}'}^{\gamma'}), \quad (5)$$

where $\Delta_{\vec{r}\vec{r}'} = f_{\vec{r}\sigma}^\dagger i \tau_{\sigma\sigma'}^\gamma f_{\vec{r}'\sigma'}$ (singlet pairing), $t_{\vec{r}\vec{r}'}^\gamma = f_{\vec{r}\sigma}^\dagger [i \hat{\tau}^\gamma \hat{\tau}^\gamma]_{\sigma\sigma'} f_{\vec{r}'\sigma'}$ (triplet pairing), $\chi_{\vec{r}\vec{r}'} = f_{\vec{r}\sigma}^\dagger f_{\vec{r}'\sigma'}$ (spin-conserving exchange term), $e_{\vec{r}\vec{r}'}^\gamma = f_{\vec{r}\sigma}^\dagger \tau_{\sigma\sigma'}^\gamma f_{\vec{r}'\sigma'}$ (spin-nonconserving exchange term). Summation over γ in Eq. (5) gives a Heisenberg term. Then, the mean-field decoupling is introduced to terms having the negative coefficient. This recovers the previous mean-field schemes [30–32]. Different decoupling schemes are also used in the literatures [13,14,33]. The full expression of the mean-field Hamiltonian is given in Ref. [24].

We remark on the AFM Kitaev limit of the undoped t_{2g}^5 model. For this limit, we looked for self-consistent mean-field solutions which respect the underlying lattice symmetry. Such a solution was found to be given by $-\langle \chi_{x,y,z} \rangle = -\langle e_z^z \rangle = \langle t_x^x \rangle = i \langle t_y^y \rangle = 0.3812i$ and

$-\langle e_x^z \rangle = -\langle e_y^z \rangle = \langle t_y^x \rangle = \langle t_z^x \rangle = i \langle t_x^y \rangle = i \langle t_z^y \rangle = -0.1188i$ with the other order parameters and the chemical potential being zero. Here, the notation is simplified by replacing the subscript $\vec{r}\vec{r}'$ with the bond index $\rho = x, y, z$ connecting the sites $\vec{r} \in A$ and $\vec{r}' \in B$; $\vec{r}_\rho = \vec{r}' - \vec{r}$. It is remarkable that this mean-field solution gives the spinon dispersion relation identical to that reported for the FM Kitaev model [24,32]; i.e., the ground state of the Kitaev model does not depend on the signs of the exchange constants [6]. The current *Ansatz* corresponds to the gauge used in Refs. [13,32], and correctly describes a Z_2 SL.

Doping effects.—We consider hopping matrices projected into neighboring Kramers doublets. In this representation, the hopping matrices are diagonal in the isospin index σ : $H_t = -\tilde{t} \sum_{\langle \vec{r}\vec{r}' \rangle \sigma} (c_{\vec{r}\sigma}^\dagger c_{\vec{r}'\sigma} + \text{H.c.})$. The hopping amplitude is renormalized according to the relative weight of the wave functions as $\tilde{t} = \frac{2}{3}(t_\pi + \frac{1}{2}t_\delta)$ [$\frac{1}{2}(t_\sigma + t_\delta)$] for the t_{2g}^5 [$e_g^{1,3}$] systems. The double occupation is prohibited due to the strong repulsive interactions for c operators. This effect at finite doping can be treated by introducing two bosonic auxiliary particles $b_{1,2}$ as $c_{\vec{r}\sigma} \Rightarrow \frac{1}{\sqrt{2}}(b_{\vec{r}1}^\dagger f_{\vec{r}\sigma} + \sigma b_{\vec{r}2}^\dagger f_{\vec{r}\sigma}^\dagger)$ (Ref. [30]) with the $SU(2)$ singlet condition $K_{\vec{r}}^\gamma = \frac{1}{4} \text{Tr} F_{\vec{r}} \hat{\tau}^\gamma F_{\vec{r}}^\dagger - \frac{1}{4} \text{Tr} \hat{\tau}^z B_{\vec{r}}^\dagger \hat{\tau}^\gamma B_{\vec{r}} = 0$. Here, $F_{\vec{r}} = \begin{pmatrix} f_{\vec{r}1} & -f_{\vec{r}1}^\dagger \\ f_{\vec{r}2} & f_{\vec{r}2}^\dagger \end{pmatrix}$ and $B_{\vec{r}} = \begin{pmatrix} b_{\vec{r}1}^\dagger & -b_{\vec{r}2} \\ b_{\vec{r}2}^\dagger & b_{\vec{r}1} \end{pmatrix}$ (Ref. [13]), and the global constraints $\langle K^\gamma \rangle = 0$ are imposed by $SU(2)$ gauge potentials a^γ . Doped carriers can be either holes or electrons, and the effect is symmetric for our model. We focus on the low-doping regime at zero temperature and assume that all bosons are condensed, i.e., $\delta = \sum_\nu \langle b_{\nu\vec{r}}^\dagger b_{\nu\vec{r}} \rangle \approx \sum_\nu | \langle b_{\nu\vec{r}} \rangle |^2$ and $\langle b_{\nu\vec{r} \in A} \rangle = (\pm i) \langle b_{\nu\vec{r} \in B} \rangle$, arriving at the mean-field hopping term: $H_t^{\text{MF}} = -\frac{\delta}{2} \tilde{t} \sum_{\langle \vec{r}\vec{r}' \rangle \sigma} \{ (\mp i) f_{\vec{r}\sigma}^\dagger f_{\vec{r}'\sigma} + \text{H.c.} \}$. The imaginary number i arises when the Bose condensation acquires the sublattice-dependent phase [13].

Many mean-field parameters have to be solved self-consistently. In order to make the problem tractable, we focus on the following five *Ansätze* which respect the sixfold rotational symmetry of the underlying lattice. The first *Ansatz*, termed p SC₁, is adiabatically connected to the mean-field solution in the Kitaev limit given above. Here, the relative phase $\pm i$ is required between the Bose condensation at sublattices A and B with the $SU(2)$ gauge potentials $a^x = a^y = a^z$ [13,24]. The second *Ansatz* is a p SC, termed p SC₂, the third one is a singlet SC with the s wave paring, and the fourth one is a singlet SC with the $d + id$ pairing. For the latter three *Ansätze*, we further assume that (1) order parameters $\langle e_\rho^\gamma \rangle$ are zero because these indeed become zero at large dopings, (2) the Bose condensation does not introduce a phase factor, and (3) the exchange term is symmetric $\langle \chi_\rho \rangle = \langle \chi \rangle$ and real. Thus, these *Ansätze* are regarded as BCS-type weak

coupling SCs. For the FM Ising case, magnetically ordered states with finite $\langle e^z_\rho \rangle = \langle e^z \rangle$ are considered as the fifth *Ansatz*.

Because of the constraint $a^x = a^y = a^z$, the spinon density $\langle f_{\bar{\sigma}}^\dagger f_{\bar{\sigma}} \rangle$ differs from the “real” electron density $\langle c_{\bar{\sigma}}^\dagger c_{\bar{\sigma}} \rangle$ in the p SC₁ phase and a normal phase ($\langle t_\rho^\gamma \rangle = \langle e_\rho^\gamma \rangle = \langle \Delta_\rho \rangle = 0$) adjacent to it. In many cases, such a normal phase has slightly lower energy than the other SC *Ansätze*. We discard such a solution as it is an artifact by the constraint.

The schematic phase diagrams for the doped AKAH model and FIAH model are shown in Figs. 3(a) and 3(b), respectively, as a function of δ and α . Here, to see various phases clearly, we chose the interaction strength as $J_K + J_H = t_\pi + \frac{1}{2}t_\delta$ and $J_I + J_H = t_\sigma + t_\delta$. For the AKAH model, the p SC₁ phase is stabilized at $\alpha \sim 1$ and $\delta \sim 0$. Its area is quite small as its stability is intimately connected to that of the Z_2 spin liquid. The large area is covered by the singlet SCs, $d + id$ phases at small δ and s at large δ . This behavior results from the fact that the AFM Heisenberg term dominates the low-energy properties. For the FM Ising case, the (111) FM phase is stabilized in the large- α and small- δ regime. The p SC₂ phase is also

stabilized from the weak coupling mechanism but is found to exist only as a metastable phase.

The p SC₁ phase is characterized by the dispersive χ^0 Majorana mode and the weakly dispersive $\chi^{x,y,z}$ modes. At finite δ , all modes are gapped by the mixing between different Majorana modes due to the finite gauge potential $a^{x,y}$. This results in the finite Chern number +1.

In the (111) FM, spin polarization is 100% at $\delta = 0$ as in the exact diagonalization result. This large spin polarization persists up to relatively large δ as carriers can move without disturbing the spin ordering. The (111) FM area is extended to smaller α at $\delta \neq 0$ because the mean-field *Ansatz* for the (111) FM is closer to the true ground state at $\delta = 0$ than that for the $d + id$. Since α is reduced by the direct dd transfers, the unconventional $d + id$ SC is the most probable candidate induced by carrier doping.

Discussion.—We now discuss the possible experimental realization of our model systems. A (111) bilayer of SrIrO₃ (Ref. [34]) would be a good candidate for our AKAH model for t_{2g}^5 systems. Also, the FIAH model might be realized in a (111) bilayer of palladium oxide LaPdO₃ (Ref. [35]). This $4d^7(t_{2g}^6 e_g^1)$ electron system consists of nearly undistorted PdO₆ octahedra and is expected to have a stronger SOC than $3d$ counterparts such as LaNiO₃. Carrier doping would be achieved by partially substituting Ir by Ru or Os (hole doping) or Sr by La (electron doping) for SrIrO₃ and La by Sr (hole doping) or Pd by Ag or Au (electron doping) for LaPdO₃. It is yet to be clarified whether SrIrO₃ and LaPdO₃ are in the strong coupling regime, resulting in Mott insulators, or in the weak coupling regime, resulting in spin Hall insulators or topological metals [18]. Even if these systems are in the Mott regime, the Kitaev SL may not be realized. But carrier doping would induce novel SC phases with $d + id$ symmetry.

For deriving effective models, the energy hierarchy is assumed as $U \gg \lambda \gg t$. Whether or not such a condition is realized in real materials remains to be examined. However, the effective transfer intensity is suppressed by correlations, and the corresponding hierarchy could be achieved self-consistently as discussed in Ref. [2]. (111) bilayers of perovskite oxides are plausible as the d bands are relatively narrow (see, for example, band structures in Ref. [18]). The form of the nearest-neighbor interaction should not be altered even if the above hierarchy is broken as long as the local crystal field is maintained and the interactions are expressed in terms of $S = 1/2$ isospins because it relies on the symmetry and the spin conservation.

Realizing Z_2 SL and p SC phases may be preferable for fault tolerant topological computations. Within the current models, these phases are hard to achieve. For this purpose, an alternative route would be looking for systems with the FM Heisenberg interaction with which the parameter spaces for the p SC phases in the doped systems are wider [28].

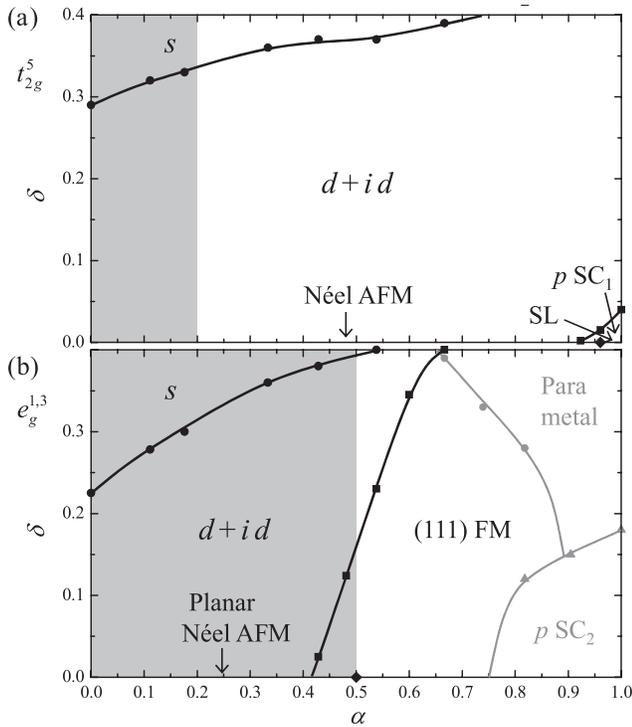


FIG. 3. Schematic phase diagrams for the doped AKAH model (a) and FIAH model (b) as a function of δ and α . Parameters are taken as $J_K + J_H = t_\pi + \frac{1}{2}t_\delta$ and $J_I + J_H = t_\sigma + t_\delta$. Phase boundaries at finite δ are the results of the $SU(2)$ SBMF, while those at $\delta = 0$ are results of the exact diagonalization. Shaded areas are the parameter ranges for $0 < 3I < U$ with $t_\delta = 0$. Light lines in (b) are phase boundaries when the FM ordering is suppressed.

To summarize, we studied the properties of Mott insulators realized in (111) bilayers of TMOs with a strong SOC. The low-energy effective models for such insulators consist of the anisotropic interaction and the AFM Heisenberg interaction. The former is of AFM Kitaev type for the t_{2g}^5 systems and FM Ising type for the $e_g^{1,3}$ systems. In both cases, large parameter spaces are characterized by magnetic long-range orderings with a narrow window for the SL regime in the t_{2g}^5 systems. Yet, carrier doping was found to make the physics of the current models more interesting by inducing unconventional SC phases in both cases. The most probable candidate is the singlet SC with the $d + id$ symmetry. In light of a weak SOC limit (Refs. [19,20]) and a strong coupling limit (Ref. [36]), TMO (111) bilayers would provide even richer quantum behavior as a function of Coulomb interactions, the SOC, and carrier doping.

We thank D. Xiao, Y. Ran, and G. Khaliullin for their fruitful discussions. This research was supported by the U.S. Department of Energy, Basic Energy Sciences, Materials Sciences and Engineering Division.

*okapon@ornl.gov

- [1] B. J. Kim, H. Jin, S. J. Moon, J.-Y. Kim, B.-G. Park, C. S. Leem, J. Yu, T. W. Noh, C. Kim, S.-J. Oh, J.-H. Park, V. Durairaj, G. Cao, and E. Rotenberg, *Phys. Rev. Lett.* **101**, 076402 (2008).
- [2] D. Pesin and L. Balents, *Nat. Phys.* **6**, 376 (2010).
- [3] F. Wang and T. Senthil, *Phys. Rev. Lett.* **106**, 136402 (2011).
- [4] A. Shitade, H. Katsura, J. Kuneš, X.-L. Qi, S.-C. Zhang, and N. Nagaosa, *Phys. Rev. Lett.* **102**, 256403 (2009).
- [5] J. Chaloupka, G. Jackeli, and G. Khaliullin, *Phys. Rev. Lett.* **105**, 027204 (2010).
- [6] A. Kitaev, *Ann. Phys. (N.Y.)* **321**, 2 (2006).
- [7] Y. Singh and P. Gegenwart, *Phys. Rev. B* **82**, 064412 (2010).
- [8] X. Liu, T. Berlijn, W.-G. Yin, W. Ku, A. Tsvelik, Y.-J. Kim, H. Gretarsson, Y. Singh, P. Gegenwart, and J. P. Hill, *Phys. Rev. B* **83**, 220403 (2011).
- [9] F. Ye, S. Chi, H. Cao, B. C. Chakoumakos, J. A. Fernandez-Baca, R. Custelcean, T. F. Qi, O. B. Korneta, and G. Cao, *Phys. Rev. B* **85**, 180403 (2012).
- [10] Y. Singh, S. Manni, J. Reuther, T. Berlijn, R. Thomale, W. Ku, S. Trebst, and P. Gegenwart, *Phys. Rev. Lett.* **108**, 127203 (2012).
- [11] S. K. Choi, R. Coldea, A. N. Kolmogorov, T. Lancaster, I. I. Mazin, S. J. Blundell, P. G. Radaelli, Y. Singh, P. Gegenwart, K. R. Choi, S.-W. Cheong, P. J. Baker, C. Stock, and J. Taylor, *Phys. Rev. Lett.* **108**, 127204 (2012).
- [12] I. Kimchi and Y.-Z. You, *Phys. Rev. B* **84**, 180407 (2011).
- [13] Y.-Z. You, I. Kimchi, and A. Vishwanath, *Phys. Rev. B* **86**, 085145 (2012).
- [14] T. Hyart, A. R. Wright, G. Khaliullin, and B. Rosenow, *Phys. Rev. B* **85**, 140510 (2012).
- [15] F. D. M. Haldane, *Phys. Rev. Lett.* **61**, 2015 (1988).
- [16] C. L. Kane and E. J. Mele, *Phys. Rev. Lett.* **95**, 146802 (2005).
- [17] S. Raghu, X.-L. Qi, C. Honerkamp, and S.-C. Zhang, *Phys. Rev. Lett.* **100**, 156401 (2008).
- [18] D. Xiao, W. Zhu, Y. Ran, N. Nagaosa, and S. Okamoto, *Nat. Commun.* **2**, 596 (2011).
- [19] A. Rüegg and G. A. Fiete, *Phys. Rev. B* **84**, 201103 (2011).
- [20] K.-Y. Yang, W. Zhu, D. Xiao, S. Okamoto, Z. Wang, and Y. Ran, *Phys. Rev. B* **84**, 201104 (2011).
- [21] For the latest development, see H. Y. Hwang, Y. Iwasa, M. Kawasaki, B. Keimer, N. Nagaosa, and Y. Tokura, *Nat. Mater.* **11**, 103 (2012).
- [22] With the strong SOC, t_{2g}^1 systems are described in terms of effective angular momentum $J_{\text{eff}} = 3/2$.
- [23] J. C. Slater and G. F. Koster, *Phys. Rev.* **94**, 1498 (1954).
- [24] See Supplemental Material at <http://link.aps.org/supplemental/10.1103/PhysRevLett.110.066403> for more information.
- [25] G. Jackeli and G. Khaliullin, *Phys. Rev. Lett.* **102**, 017205 (2009).
- [26] G. Khaliullin, *Prog. Theor. Phys. Suppl.* **160**, 155 (2005).
- [27] J. Chaloupka, G. Jackeli, and G. Khaliullin, *arXiv:1209.5100*.
- [28] S. Okamoto, *arXiv:1212.5218*.
- [29] A. M. Black-Schaffer and S. Doniach, *Phys. Rev. B* **75**, 134512 (2007).
- [30] P. A. Lee, N. Nagaosa, and X.-G. Wen, *Rev. Mod. Phys.* **78**, 17 (2006).
- [31] R. Shindou and T. Momoi, *Phys. Rev. B* **80**, 064410 (2009).
- [32] R. Schaffer, S. Bhattacharjee, and Y.-B. Kim, *Phys. Rev. B* **86**, 224417 (2012).
- [33] F. J. Burnell and C. Nayak, *Phys. Rev. B* **84**, 125125 (2011).
- [34] G. Cao, V. Durairaj, S. Chikara, L. E. DeLong, S. Parkin, and P. Schlottmann, *Phys. Rev. B* **76**, 100402(R) (2007).
- [35] S.-J. Kim, S. Lemaux, G. Demazeau, J.-Y. Kim, and J.-H. Choy, *J. Am. Chem. Soc.* **123**, 10413 (2001); *J. Mater. Chem.* **12**, 995 (2002).
- [36] K. I. Kugel and D. I. Khomskii, *Sov. Phys. Usp.* **25**, 231 (1982); *Sov. Phys. Solid State* **17**, 285 (1975).